

Study of BaTiO₃ ceramics doped with Mn and Ce or Nb and Sr

A.M.Slipenyuk, M.D.Glinchuk, I.P.Bykov, L.P.Yurchenko,
V.A.Mikheev, O.A.Frenkel, V.D.Tkachenko, E.P.Garmash

Institute for Problems of Materials Science
of the National Academy of Sciences of Ukraine,
3 Krjijanovskogo Str., 03680 Kiev-142, Ukraine

Received December 12, 2002, in final form April 8, 2003

ESR study of BaTiO₃ ferroelectrics doped with cerium or with niobium and strontium, both types of samples being doped with manganese, was performed at room temperature. In the samples of the first type the most intensive line with g -factor 1.9612 was shown to originate from paramagnetic center Ti³⁺–Ce³⁺. The small intensity line was related to Fe³⁺–V_O center, which can be unavoidable impurity in BaTiO₃.

In the samples doped with strontium, the six lines intensive spectrum, which corresponds to hyperfine structure of Mn²⁺, was observed. The intensity of the spectrum was shown to decrease with strontium concentration increase. This effect was supposed to be related to the decrease of the grain sizes that results in migration of manganese and, possibly, niobium ions. The influence of these impurities, of their charge states and positions in crystalline lattice of BaTiO₃ on the PTCR effect is discussed.

Key words: *BaTiO₃ ceramics, impurities, positive temperature coefficient of resistivity*

PACS: *72.80.Sk, 76.30.Fc, 77.84.Dy*

1. Introduction

The positive temperature coefficient of resistivity (PTCR) effect in BaTiO₃ ceramics is widely regarded as a grain boundary-controlled phenomenon [1,2]. In spite of numerous studies of the factors influencing the PTCR effect, it is still poorly characterized and technological advances in optimizing the PTCR profile have taken place ahead of a better understanding of the underlying scientific phenomenon. Various theories [1,3–5] of the PTCR effect have been proposed. One of the most important problem which is still unsolved is the influence of the impurities on this effect. This problem was studied by several authors [6–8] to clear up the states of the impurities in BaTiO₃ ceramics and their influence on the materials' properties. It was shown (see e.g. [9,10]) that PTCR effect in BaTiO₃ ceramics, doped with

donors (e.g. rare-earth ions or Nb^{5+} ions) can be significantly increased by adding small amounts of 3d-ions, the most effective among them being Cu^{2+} or Mn^{2+} . This additional doping leads to an increase of $\rho_{\text{max}}/\rho_{\text{min}}$ ratio (ρ is electric resistivity) which is the most important feature to be applied. On the other hand, the dopants are known to influence the temperature of the ferroelectric phase transition (T_c), e.g. lead and zirconium additives shift T_c to the range of larger and smaller temperatures, respectively. From technological point of view, it is worth mentioning that the impurities influence the kinetics of the ceramics sintering since the diffusion processes depend on the defects and the impurities in the lattices. Therefore, the investigations of the type of the defects and of the impurities, their charge state and position in the lattice play a decisive role in understanding the nature of the PTCR effect and in optimizing BaTiO_3 ceramics properties.

The main goal of this work was the investigation of BaTiO_3 ceramics doped by several impurities (Ce and Mn or Nb, Sr and Mn) by measurements of the ESR spectra and temperature dependence of electroresistivity. The X-ray and electron-microscopy analysis were also used.

2. Experimental details

The samples of posistor ceramics of BaTiO_3 were fabricated from BaCO_3 and TiO_2 of high purity. The doping was made by addition of SrCO_3 , Nb_2O_5 and MnCl_2 . The synthesis was performed by conventional technology at $T = 1380$ °C during one hour. The ceramic samples were pellets with sizes: $D = 12$ mm, $h = 2$ mm. The phase content of the ceramics was controlled by X-ray diffraction method. The electric resistivity ρ of the investigated samples was measured by a four-point method. The layers of In and pure graphite were used as electrodes with the surface resistivity smaller than $0.5 \Omega\text{m}/\text{cm}^2$.

ESR spectra were recorded at 9.4 GHz spectrometer at room temperature. The measurements were carried out on the powders of the studied samples.

3. The results of measurements

1. X-ray diffraction investigations of BaTiO_3 samples doped with Sr, Ce, Nb and Mn were carried out. The decrease of peaks 422 and 244 splitting at Sr concentration $x > 0.35$ along with asymmetrical peak broadening may be the consequence of coexistence of cubic and tetragonal phases in the ceramics. These results are similar to those obtained in previous works (see for instance [6,7,10]).
2. The ESR spectra observed in the BaTiO_3 ceramics doped with cerium and with cerium and manganese are depicted in figure 1a and 1b, respectively. The most intensive line in figure 1a has g -factor 1.9612. This line was observed earlier in several works, but its nature is still under discussion. In particular, it was recently shown that the line with $g = 1.961$ can be related to paramagnetic

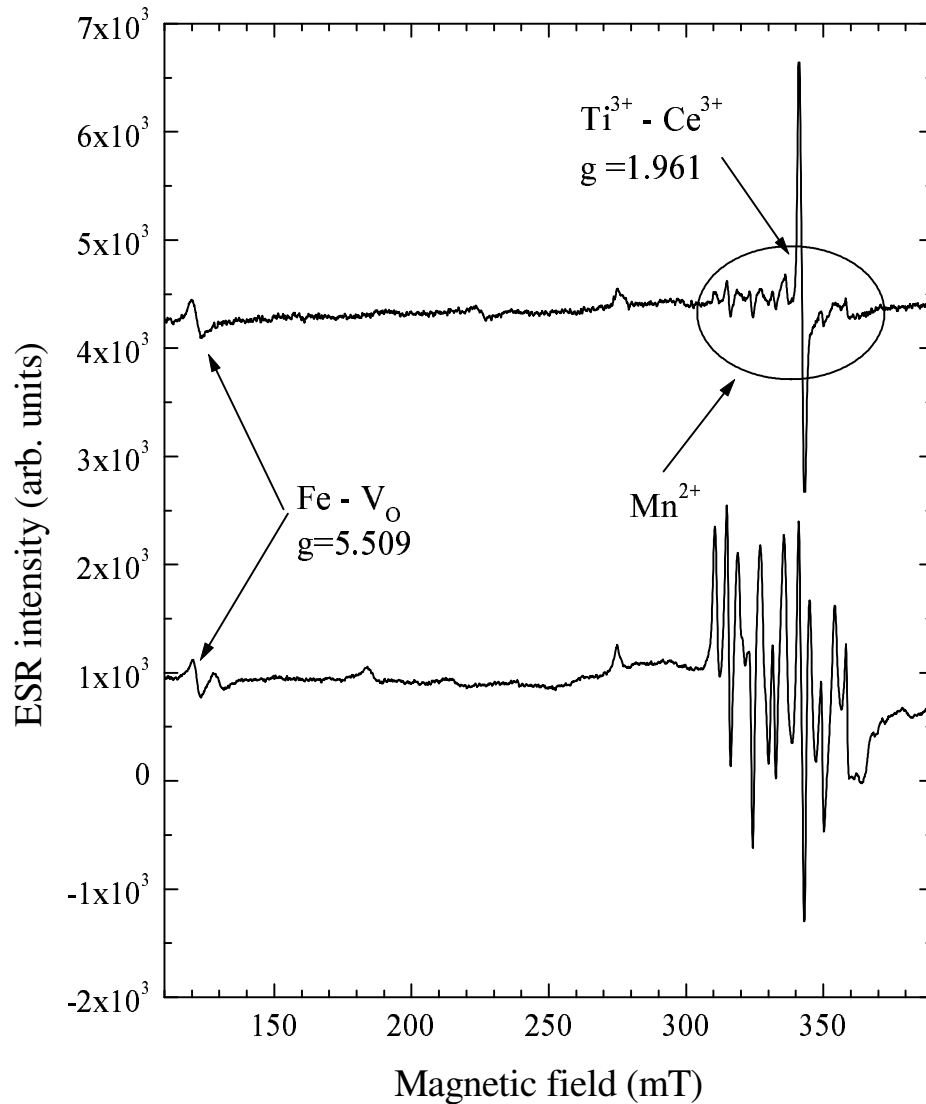


Figure 1. ESR spectra in BaTiO₃ ceramics doped with Ce₂O₃ (a), MnO and Ce₂O₃ (b).

complex Ti³⁺-Ln³⁺ (Ln³⁺ is a rare-earth ion) [11], while in [12] it was supposed that it belongs to Ti³⁺-V_O. Another line in the spectrum has g -factor 5.549. The line with practically the same g -factor was observed earlier in the ceramic samples of BaTiO₃ doped with rare-earth ions (Y, La, Sm, Dy) [13]. This line was identified as that from paramagnetic center Fe³⁺-V_O where iron ions were unavoidable impurities. The intensity of the line with $g \approx 1.9612$ slightly decreased while the line with $g = 5.549$ practically conserves its parameters.

The small intensive lines in the vicinity of $g \approx 2$ observed in Ce-doped BaTiO₃ may be related to unavoidable impurity of manganese, which is often present in BaTiO₃ ceramics. The confirmation of this supposition was obtained from the measurements of the BaTiO₃ samples doped both with Ce and Mn (see figure 1b), where the intensity of the ESR lines near $g \approx 2$ strongly increased.

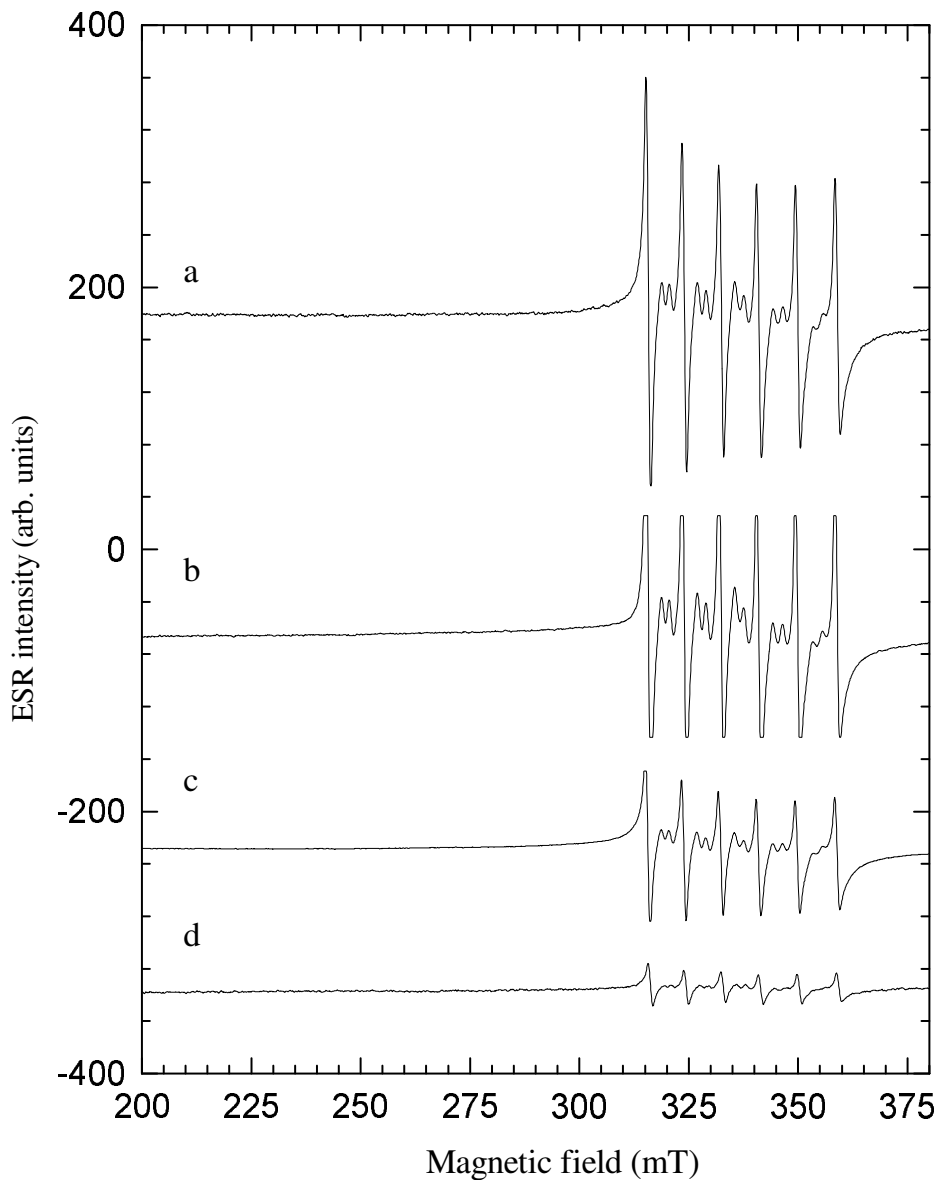


Figure 2. ESR spectra of Mn^{2+} in $\text{Ba}_{1-x}\text{Sr}_x\text{TiO}_3$ ceramics doped with MnO and Nb_2O_5 : (a) $x = 0.2$, (b) $x = 0.3$, (c) $x = 0.35$, (d) $x = 0.4$.

The characteristic hyperfine structure of the spectra speaks in favor of the statement that this spectrum belongs to Mn^{2+} ions.

The spectrum of the Mn^{2+} with six hyperfine lines was clearly observed in the BaTiO_3 samples doped with Sr, Nb and Mn ions (see figure 2). One can see that the intensity of the Mn^{2+} spectrum decreases with the increase of strontium concentration. The dependence of Mn^{2+} spectrum intensity on Sr concentration is depicted in figure 3. Note that we did not observe the spectrum of the $\text{Fe}^{3+}-\text{V}_\text{O}$ in these samples.

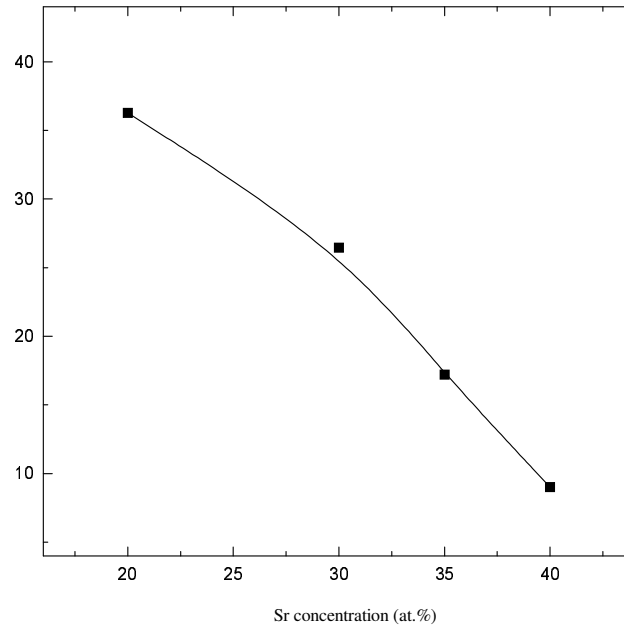


Figure 3. Dependence of Mn²⁺ ESR spectra intensity in Ba_{1-x}Sr_xTiO₃ doped with MnO and Nb₂O₅ on strontium concentration.

3. The temperature dependence of the resistivity of Ba_{1-x}Sr_xTiO₃ samples doped with 0.3 at. % of Nb and 0.1 at. % of Mn is depicted in figure 4. One can see that at room temperature the resistivity of all the samples is low and it slightly changes from 2.5 kΩm to 9.8 kΩm. The temperature of the ferroelectric/paraelectric phase transition depends on Sr content. In particular, at $x = 0.4$ T_c shifts at more than 60 degrees. Therefore, Sr-doped BaTiO₃ samples show the PTCR effect close to a room temperature.

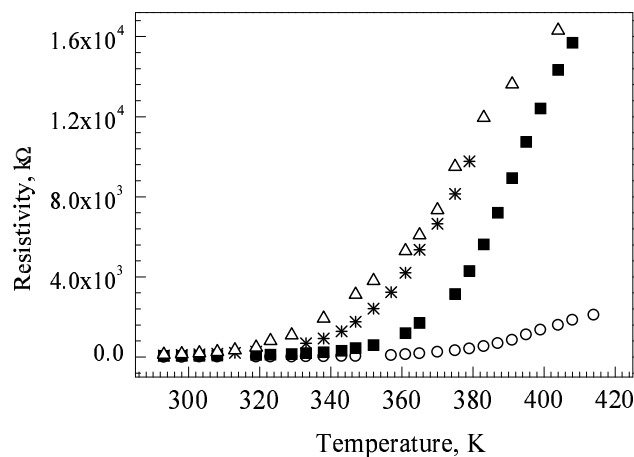


Figure 4. Temperature dependence of resistivity of barium titanate ceramic samples with different strontium content x : \circ – 0.2, \blacksquare – 0.3, $*$ – 0.35, \triangle – 0.4.

4. Discussion

The most probable Ce^{3+} ions are substitute for Ba^{2+} , because the ionic radius of Ce^{3+} ($r = 1.034 \text{ \AA}$) is much larger than that of Ti^{4+} ($r = 0.68 \text{ \AA}$). For the sake of excess positive charge compensation the $\text{Ti}^{3+}\text{-Ce}^{3+}$ center can appear. Since Ti^{3+} is a paramagnetic ion with spin $S = 1/2$, the ESR line of Ti related center will arise. We observed similar spectra in BaTiO_3 ceramics doped by rare-earth ions [11]. Since the correlation between ESR spectra intensity and rare-earth ions concentration was revealed, the spectra were ascribed to $\text{Ti}^{3+}\text{-Ln}^{3+}$ centers, where Ln^{3+} is a rare-earth ion. Moreover, there was shown a correlation of these centers ESR-line intensity and the conductivity behaviour. Namely, the ESR spectra intensity increase corresponds to the increase of conductivity and vice versa. These facts made it possible to suppose that the ESR line with $g = 1.9612$ belongs to $\text{Ti}^{3+}\text{-Ce}^{3+}$ related centers and namely they lead to semiconductor properties of BaTiO_3 .

In the Nb-doped BaTiO_3 samples, the situation differs from the case considered above. The Nb^{5+} ionic radius (0.69 \AA) is much smaller than that of Ce^{3+} and close to ionic radius of Ti^{4+} . Therefore, Nb^{5+} substitutes Ti^{4+} in the lattice producing excessive positive charge. For an excessive charge compensation the $\text{Ti}^{3+}\text{-Nb}^{5+}$ centers can arise. However, due to an intensive Mn^{2+} spectrum it appeared impossible to observe the ESR line of these centers. On the other hand, for an excessive positive charge compensation, the $\text{Nb}^{5+}\text{-Mn}^{3+}$ centers can also arise. Unfortunately, Mn^{3+} is ESR silent, so it appeared impossible to check this supposition. Usually only the spectra of Mn^{2+} ($S = 5/2$) and Mn^{4+} ($S = 3/2$) can be observed.

In pure BaTiO_3 ceramics it appeared possible to observe the Mn^{2+} spectrum in low temperature ferroelectric phases (orthorhombic and rhombohedral) or in paraelectric phase ($T > T_c$). To observe it at room temperature (tetragonal phase), the doping of BaTiO_3 is necessary to make a lattice distortion and to change a local symmetry. Such Mn^{2+} spectrum was observed earlier at room temperature in La- and Mn-doped BaTiO_3 samples [14], and the spectra were described by $g_{\parallel} = 2.028$ and $g_{\perp} = 2.0024$. Above T_c only one spectrum with larger intensity was recorded. In our measurements of Nb-, Sr-, Ce- and Mn-doped BaTiO_3 ceramics Mn^{2+} ESR spectra were observed at room temperature. The strong decrease of Mn^{2+} ESR intensity with the increase of Sr concentration can be related to the decrease of the grain size as the electron microscopy has shown. Since the spectra that we observed originate from Mn^{2+} ions in the grains and the decrease of grain sizes causes a decrease of ESR intensity. The dependence of the charge state of impurity ions on their position in the grain or intergrain space was observed earlier in PZT ceramics [15–17].

The measurements of the electric resistivity had shown that at room temperature the resistivity increases by an order of magnitude with the increase of Sr concentration. The temperature of PTCR effect strongly depends on Sr content and, at $x = 0.4$, a resistivity jump occurs at $60 \text{ }^{\circ}\text{C}$ which is very important for application in the modern technologies.

In conclusion we want to underline that this is part of a larger study to investigate the mechanisms behind the positive temperature coefficient of resistivity

observed in the doped BaTiO₃ ceramics (see [11,13,18,19]). In the present work, we studied the Sr, Ce, Nb and Mn influence on the BaTiO₃ properties. Both Nb and Ce ions provide the semiconductor properties of the BaTiO₃ ceramics, and the Mn ions create the centers which are the traps of charge carriers. SrTiO₃ is an incipient ferroelectric with $T_C(\text{SrTiO}_3) \ll T_C(\text{BaTiO}_3)$. Therefore, the BaTiO₃ doping with strontium titanate leads to T_C shift to the low temperature range. In this work, on the basis of our previous studies, there was theoretically predicted the type and concentrations of dopants in BaTiO₃ ceramics, which provide the PTCR effect at room temperature. Corresponding samples were manufactured and there was experimentally confirmed the existence of the effect of positive temperature coefficient of resistivity at temperatures close to a room temperature under strontium content over 35 at.% and Ce, Nb and Mn concentration 0.1–0.3 at.%.

It is obvious that the doping of BaTiO₃ ceramics with several impurities can be useful in managing the value of PTCR effect as well as the temperature range of the occurrence of this effect.

5. Acknowledgements

Authors are acknowledged to Dr. G.S.Oleynik for electron-microscopy analysis of the samples.

References

1. Heywang W. // J. Am. Ceram. Soc., 1964, vol. 47, p. 484–493.
2. Goodman G. // J. Am. Ceram. Soc., 1963, vol. 46, p. 45–49.
3. Jonker G.H. // Solid State Electron., 1964, vol. 7, p. 895–899.
4. Jonker G.H. // Mater. Res. Bull., 1969, vol. 2, p. 401–405.
5. Daniels J., Haerdtl K.H., Wernicke R. // Philips. Tech. Rev., 1977, vol. 38, p. 73–79.
6. Ueoka H. // Ferroelectrics, 1974, vol. 7, p. 351–356.
7. Ikushima H., Hayakawa S. // Natl. Tech. Rept., 1967, vol. 13, p. 209–216.
8. Matsuoka T., Fujimura M., Matsuo Y., Hayakawa S. // J. Am. Ceram. Soc., 1972, vol. 55, p. 108–116.
9. Matsuoka T., Fujimura M., Matsuo Y., Hayakawa S. // Natl. Tech. Rept., 1975, vol. 21, p. 329–339.
10. Jida S., Miki T. // J. Appl. Phys., 1996, vol. 80, p. 5234–5245.
11. Glinchuk M.D., Bykov I.P., Kornienko S.M., Laguta V.V., Slipenyuk A.M. et al. // Journal of Materials Chemistry, 2000, vol. 10, p. 941–948.
12. Kutty T.R.N., Muragaraj P., Gajbhiye N.S. // Mater. Lett., 1984, vol. 2, p. 396–399.
13. Kornienko S.M., Bykov I.P., Glinchuk M.D., Laguta V.V., Belous A.G., Jastrabik L. // FTT, 1999, vol. 41, p. 1838–1842 (in Russian).
14. Kutty T.R.N., Muragaraj P. // Mater. Lett., 1985, vol. 3, p. 195–198.
15. Bykov I.P., Glinchuk M.D., Skorokhod V.V. // FTT, 1992, vol. 34, p. 1353–1358 (in Russian).
16. Boudys M., Mejezchleb K. // Ferroelectrics, 1992, vol. 126, p. 247–254.

17. Glinchuk M.D., Bykov I.P., Skorokhod V.V., Kala T. // *Ferroelectrics*, 1992, vol. 131, p. 223–227.
18. Slipenyuk A.M., Glinchuk M.D., Bykov I.P., Laguta V.V., Bilous A.G., V'yunov O.I. // *Ferroelectrics*, 2001, vol. 254, p. 349–357.
19. Slipenyuk A.M., Glinchuk M.D., Laguta V.V., Bykov I.P., Bilous A.G., V'yunov O.I. // *Ferroelectrics*, 2001, vol. 254, p. 383–391.

Дослідження кераміки BaTiO₃ легованої Mn та Ce або Nb та Sr

А.М.Сліпенюк, М.Д.Глинчук, І.П.Биков, Л.П.Юрченко,
В.А.Міхеев, О.А.Френкель, В.Д.Ткаченко, Є.П.Гармаш

Інститут проблем матеріалознавства НАН України,
03680 Київ-142, вул. Кржижановського, 3

Отримано 12 грудня 2002 р., в остаточному вигляді – 8 квітня 2003 р.

Представлено результати ЕПР досліджень сегнетоелектричної кераміки BaTiO₃ двох серій: легованої церієм та марганцем або ніобієм, стронцієм та марганцем, при кімнатній температурі. Показано, що у зразках першої серії найбільш інтенсивна лінія з *g*-фактором 1.9612 належить до парамагнітного центру Ti³⁺–Ce³⁺. Лінії малої інтенсивності належать до центру Fe³⁺–V_O (пов'язаного з неконтрольованою домішкою заліза у зразках) та до іону Mn²⁺.

В другій серії зразків спостерігався спектр, який відповідає надтонкій структурі іону Mn²⁺. Інтенсивність цього спектру зменшувалась із збільшенням концентрації стронцію. Можливо цей ефект пов'язаний із зменшенням розмірів зерен та міграцією марганцю та, можливо ніобію, у міжзерновий простір. Обговорюється вплив домішок, їх зарядового стану та позиції у кристалічній ґратці на ефект позитивного температурного коефіцієнту опору.

Ключові слова: кераміка BaTiO₃, домішки, ЕПР, позисторний ефект

PACS: 72.80.Sk, 76.30.Fc, 77.84.Dy